

# WOOD AND FIBER SCIENCE

(ISSN 0735-6161)

Volume 37 • January 2005 • Number 1

*JOURNAL OF THE*  
SOCIETY OF  
**WOOD** **SWST**  
SCIENCE AND TECHNOLOGY

# SOCIETY OF WOOD SCIENCE AND TECHNOLOGY

## 2004–2005 Officers of the Society

*President:* AUDREY ZINK-SHARP, Virginia Tech, Blacksburg, VA 24061

*Past President:* DOUGLAS D. STOKKE, Iowa State University, Ames, IA 50011

*President-Elect:* PAUL M. SMITH, Pennsylvania State University, University Park, PA 16802

*Vice President:* DOUGLAS GARDNER, University of Maine, Orono, ME 04469

*Executive Director:* VICKI L. HERIAN, Society of Wood Science and Technology, One Gifford Pinchot Drive, Madison, WI 53726-2398

### *Directors:*

JEFF MORRELL, Oregon State University, Corvallis, OR 97331

J. DANIEL DOLAN, Washington State University, Pullman, WA 99164

ROBERT L. BEAUREGARD, Université Laval, Sainte-Foy, Quebec, Canada G1K 7P4

JERRY WINANDY, U.S. Forest Products Laboratory, Madison, WI 53726

## WOOD AND FIBER SCIENCE

WOOD AND FIBER SCIENCE is published quarterly in January, April, July, and October by the Society of Wood Science and Technology, One Gifford Pinchot Dr., Madison, WI 53726-2398, in cooperation with the Forest Products Society.

### *Editor*

GEZA IFJU

### *Associate Editor*

D. EARL KLINE

### *Editorial Assistant*

CAROL B. OVENS

### *Newsletter Editor*

RADO GAZO

There are three classes of membership in the Society: Members—dues \$75.00; Retired Members—dues \$40.00; Student Members—dues \$25.00. Applications for membership and information about the Society may be obtained from the Executive Director, Society of Wood Science and Technology, One Gifford Pinchot Dr., Madison, WI 53726-2398.

Institutions and individuals may subscribe to WOOD AND FIBER SCIENCE at \$250.00 per volume (four issues). New subscriptions begin with the first issue of a new volume. Single issues are \$28.00 each. Back issues may be purchased for \$10.00 each, except for 1994 and later years, which are full price. All subscriptions are to be ordered through the Executive Director. Make checks for subscriptions and membership payable to the Society of Wood Science and Technology.

The Executive Director, at the Business Office shown below, should be notified 30 days in advance of a change in address. Copies undeliverable because of address change will be destroyed. Issues lost in the mail will be replaced free if notice is received within one month of date of issue of the succeeding number.

*Printing Office:* Allen Press, Inc., P.O. Box 621, Lawrence, KS 66044, USA

*Business Office:* Society of Wood Science and Technology, One Gifford Pinchot Dr., Madison, WI 53726-2398

*Editorial Office:* Geza Ifju, Department of Wood Science and Forest Products, Brooks Forest Products Center, Virginia Tech, Blacksburg, VA 24061-0503.

**POSTMASTER:** Send address changes to the Society of Wood Science and Technology, One Gifford Pinchot Dr., Madison, WI 53726-2398

Copyright, 2005, by the Society of Wood Science and Technology

Periodicals postage paid at Madison, Wisconsin 53726-2398, USA, and at additional mailing offices.

This issue was mailed January 6, 2005

# INFORMATION FOR AUTHORS

## EDITORIAL POLICY

*Wood and Fiber Science* is the official publication of the Society of Wood Science and Technology, and accordingly publishes papers with both professional and technical content. Original papers of professional concern or research papers that add to basic understanding of wood and wood fiber or of the processing, marketing, and use of their products will be considered. Papers will be judged on the basis of their contribution of original data and ideas or interpretation or, in the case of reviews, on their currency and completeness. Any manuscript submitted must be unpublished research not being offered for publication elsewhere. Upon acceptance and publication by *Wood and Fiber Science*, a manuscript must not be published again in any form without written consent of both author and editor.

Papers will be reviewed by referees selected by the editor and will be published in approximately the order in which the final version is received. All manuscripts are to be clearly written in English with American spelling.

## FORM OF MANUSCRIPTS

Submit the manuscript in quadruplicate, double-spaced throughout, and typed with a font having 10 characters per inch. A suggested limit for the text is 5000 word equivalents. SI units should be used. The *CBE Style Manual*, Fifth Edition; *GPO Style Manual*; and *Webster's Third New International Dictionary* are useful guides for matters of form, style, and spelling. Sequence of material: Title page, abstract, keywords, text, references, tables, figure legends, and figures.

**TITLE PAGE.** Include title, each author's name and title, affiliation, and complete mailing address. Provide a condensed running head of no more than 60 letters and spaces.

**ABSTRACT.** Limit to 3% of length of article. A concise, informative results-type abstract suitable for reproduction in an abstracting journal is required.

**KEYWORDS.** List beneath abstract those keywords relating to major methods or results of study.

**TEXT.** Acknowledgments are best made in the introduction or in a separate section between conclusion and references. Make certain each figure and table is referred to, in order, in the text.

**REFERENCES.** Make all references in text by author and year of publication. For three or more authors, cite the first only and use et al. List all references alphabetically by first author under the heading REFERENCES.

- Article: MANESS, THOMAS C., AND W. STUART DONALD. 1994. The effect of log rotation on value recovery in chip and sawmills. *Wood Fiber Sci.* 26(4):546-555.
- Book: SINCLAIR, S. 1992. Forest products marketing. McGraw-Hill, New York, NY. 403 pp.
- Chapter: LEATHAM, G. F., G. C. MYERS, T. H. WEGNER, AND R. A. BLANCHETTE. 1990. Energy savings in biomechanical pulping. Pages 17-25 in T. K. Kirk and H.-M. Chang, eds. *Biotechnology in pulp and paper manufactures, applications, and fundamental investigations*. Butterworths-Heinemann, Boston, MA.
- Internet: SASSUS, F., M. FOURNIER, AND B. THIBAUT. 1995. Longitudinal growth strains and drying shrinkage in tension wood of poplars (*Populus euroamericana* cv 1214) IUFRO XX World Congress, Tampere, Finland <http://www.metla.fi/conf/iufro95abs/d5pos13.htm>. (8 June 1998).

**FOOTNOTES.** Avoid use of footnotes where possible. Number consecutively those that are necessary and type on a separate page following references.

**EQUATIONS:** All equations to be set off from the text must be numbered.

**TABLES AND FIGURES.** Tables and figures should not exceed 20% of the total length of the paper. The printed page is 145 × 200 mm. Single column is up to 68 mm. Tables and figures may be printed up to a full page in width. Each table should be on a separate sheet of paper. Figure legends should be typed double spaced on a separate sheet following the tables. Figures must be camera-ready. Figure numbers should be marked on the back of the sheet, not next to the figure.

## PAGE CHARGES

Articles are accepted for publication on the basis of scientific or technological merit. The publication cost is \$100 per page for members of SWST and \$135 per page for non-members. Changes in proof will be billed to the author at \$3.00 per line. Folded inserts, envelope inserts, and colored illustrations can be printed only when paid for by the author.

## SUBMISSION OF MANUSCRIPTS

Address all manuscripts and correspondence concerning editorial matters to the Editor, Geza Ifju, Department of Wood Science and Forest Products, Brooks Forest Products Center, Virginia Tech, Blacksburg, VA 24061-0503. In U.S., use first class mail; from other countries, use air mail.

# CHANGES IN THE CHEMICAL COMPOSITION AND SPECTROSCOPY OF LOBLOLLY PINE MEDIUM DENSITY FIBERBOARD FURNISH AS A FUNCTION OF AGE AND REFINING PRESSURE

*Stephen S. Kelley*

Principal Scientist  
National Bioenergy Center  
National Renewable Energy Laboratory  
1617 Cole Boulevard  
Golden, CO 80401

*Thomas Elder†*

Research Forest Products Technologist

and

*Leslie H. Groom†*

Project Leader, Research Forest Products Technologist  
USDA-Forest Service  
Southern Research Station  
2500 Shreveport Highway  
Pineville, LA 71360

(Received October 2003)

## ABSTRACT

Loblolly pine wood between the ages of 5–35 was refined into medium density fiberboard furnish at steam pressures from 2 to 18 bar. The effect of age and processing conditions on the properties of the fibers was assessed by wet chemical analyses, Near Infrared Spectroscopy (NIR) and powder X-ray diffraction (XRD). In general, the percentages of extractives and glucose increased, while the xylose, galactose, and mannose decreased with increasing refining pressure. There were no consistent changes in chemical composition of the refined fibers as a function of the age of the wood. The crystallinity of the refined fibers increased with both age and refining pressure. The spectroscopic and XRD data were analyzed using multivariate statistical methods, indicating a strong relationship between the spectral patterns and refining pressure.

**Keywords:** Medium density fiberboard, (MDF), near infrared spectroscopy, X-ray diffraction, partial least squares.

## INTRODUCTION

Medium density fiberboard is a nonstructural panel product, with densities of 31–50 pounds per cubic foot that are uniform throughout the panel, generally glued with urea-formaldehyde resins, and used in applications including furniture underlayment, molding and door skins

(USDA 1999). The panel furnish is manufactured by subjecting wood chips to a thermomechanical process, in which the wood is subjected to high pressure steam and then reduced to fibers by shearing the wood through a set of refiner plates. Adhesives and waxes are added to the fibers, which are subsequently pressed to specified thickness and density.

Recent studies have examined the impact of processing conditions and location within the

†Member of SWST.

tree from which the chips originated on the fundamental material properties of the fibers. These results have also been compared to the properties of the finished boards.

In a preliminary study, chips representing juvenile wood (rings 1–10) and mature wood (rings 20 and above) of a loblolly pine were processed at steam pressures of 4, 8, and 12 bar. These fibers have been analyzed with scanning electron microscopy, atomic force microscopy (Snell et al. 2001), Fourier transform infrared spectroscopy, and X-ray photoelectron spectroscopy (Rials et al. 2001). The microscopy experiments indicated an increase in surface roughness with refiner pressure, with juvenile wood fibers exhibiting a higher degree of roughness than mature ones. Quantitative measures of roughness showed that surface roughness is greatest for both tissue types at the 8 bar pressure. These results are interpreted as indicating the occurrence of different failure modes in juvenile and mature wood at differing pressures. Fiber lengths were also found to be maximized at 8 bar, with the fibers refined at 4 and 12 bar exhibiting about equal fiber lengths (Rials et al. 2001). This behavior, in which the samples refined at 8 bar differ markedly from the others, can also be observed through the determination of surface energy by inverse gas chromatography (Elder et al. 2002). Furthermore, these differences in surface level properties are consistent with the stiffness of panels made from these fibers, which were also found to be at a maximum at 8 bar (Rials et al. 2001).

The chemical composition and physical properties of wood and a variety of biomass materials have been measured with NIR spectroscopy (Hoffmeyer and Pedersen 1995; Kelley et al. 2004; McLellan et al. 1991; Newman et al. 1994; Raymond et al. 2001; Schimleck et al. 1997; Tygesen 1994; Thumm and Meder 2001). These studies have shown that all of the individual wood components, lignin, extractives, and individual sugars can be measured with NIR. Physical properties such as density, mechanical strength, and microfibril angle can also be measured with NIR (Hoffmeyer and Pedersen 1995;

Kelley et al. 2004; Thumm and Meder 2001). The bending and internal bond properties of MDF panels have also been correlated with NIR spectra (Rials et al. 2001). All of these results suggest that NIR should be useful for characterization of these MDF fibers.

Changes in the crystallinity of cellulose (Segal et al. 1959; Hu and Hsieh 1996; Hindeleh and Johnson 1972; Bang et al. 1999) and wood pulps as a function of processing conditions (Ramos et al. 1999; Goswami et al. 1996) have been reported by several authors. In work directly related to the current paper, Ahtee et al. (1980, 1983) have used X-ray diffraction to determine the crystallinity of thermomechanical pulps. Beating to various freeness levels seems to have little impact on the crystallinity, while as might be expected, it is reported that grinding in a ball mill for increasing lengths of time dramatically decreases the crystallinity.

Based on this body of prior work, the current study was undertaken to relate changes in the chemical composition and spectra of refined fibers to the refining conditions and the age of the original wood chips. The chemical composition of a subset of the fibers was measured with standard wet chemical techniques. NIR spectra of these fibers were collected to investigate the potential for using NIR to measure the chemical composition of MDF fibers and to see if the spectra could be related to processing conditions. XRD patterns were collected on a larger set of fibers to investigate the effects of the age of the wood chips and the refining conditions on the fibers.

## METHODS

### *Production of refined fibers*

Loblolly pine was collected from the Crossett Experimental Forest, and individual trees were divided into four age groups representing tissue from the pith to ring 8, rings 9–16, 17–24, and 25 and above. The wood was chipped and pressure-refined at the BioComposites Center in Bangor, Wales (Snell et al. 2001; Rials et al. 2001). The refining conditions included pres-

sures of 2, 4, 5, 6, 7, 8, 10, 12, 14, and 18 bar, providing a total of 40 samples for evaluation.

#### *Chemical analysis*

All samples were milled using a Standard Wiley knife mill with a 2-mm screen (ASTM 1999). All samples were analyzed using ASTM standard methods for whole biomass analysis (ASTM 1999). NIST Pine Standard Reference Material # 8493 was used as a reference for the determination of extractives, lignin, and carbohydrates. Analysis errors for softwood composition using these traditional wet chemical analysis methods are 0.5% for lignin and ash, 1.0% for glucose and extractives, and 1.5% for all other sugars (Milne et al. 1992).

#### *NIR measurements*

The NIR spectrometer used for method development was a Foss NIR Systems model 6500 Forage Analyzer with a sample transport module and a standard reflectance detector array that measures between 400–2500 nm. Natural product sample compartment cells in 1/4 cup size and ring cups (4-mm diameter) for small samples were used as sample holders in the transport module. This instrument has a maximum resolution of 2 nm. The fiber samples were ground using a small coffee grinder to homogenize the sample and to minimize differences in particle size. Each sample was sub-sampled three times, and the sub-sample spectra were averaged; the samples were also run in duplicate and the duplicate spectra were averaged. This provided a thoroughly representative spectrum that was used for the analysis.

#### *XRD measurements*

Powder X-ray diffraction measurements were taken on each sample, at 20 angles from 3 to 90°, using a Rigaku Miniflex X-ray Powder Diffractometer, with Cu K $\alpha$  radiation (1.54056 Å). Crystallinity indices were calculated by  $I(22^\circ)/I(18^\circ)$  (Segal et al. 1959). The complete XRD patterns, containing more than 8,500 data-

points each, were averaged along the angle axis by a factor of 20 to produce a file with 425 points for each pattern. The PLS (partial least squares) models were constructed with these averaged data sets.

#### *PLS analysis*

The spectra and XRD patterns were converted to an Unscrambler @ file (The Unscrambler 7.6, 2000). The reflectance spectra were converted to absorbance spectra in Unscrambler @. All the data sets were subjected to Multiplicative Scattering Correction (MSC) using the Unscrambler algorithms. Averaging the spectral data reduces the size of the matrix and significantly reduces the time required to compute the projection to Latent Structures (PLS) models without decreasing the quality of the models.

Given that 19 samples were subjected to wet chemical analysis, the NIR and PLS correlation models for the chemical composition were based on full cross validation, with one sample removed at a time (Gabrielsson et al. 2002; Martens and Naes 1991). The correlation coefficient and root mean square error of prediction are generated by the full cross-validation procedure. For the analyses of refining pressure and total crystallinity, 40 samples were analyzed, and the data sets were randomly divided into two groups. One group was used to construct a calibration model, using full cross-validation, and this calibration model was used to predict the properties of the second set of samples that were not included in the original model. The correlation coefficient and root mean square error of prediction are from the validation set.

### RESULTS AND DISCUSSION

#### *Changes in chemical composition*

The results of the wet chemical analysis are shown in Fig. 1a–1f. While it is well known that the chemical composition of juvenile pinewood and mature pinewood is different, there were no consistent changes in the chemical composition

for the different age classes. Thus, the four different age classes at five different refining pressures were averaged to show trends in the chemical composition as a function of refining pressure. There is a significant increase in the extractives content (Fig. 1a), and a less dramatic increase in the glucose content (Fig. 1b), with increasing refining pressure. There is a corresponding decrease in the hemicellulose sugars, xylose (Fig. 1c), galactose (Fig. 1d), and mannose (Fig. 1e) at the higher refining pressures. The lignin content remains the same as a function of refining pressure, although there is a large amount of variation between the different samples.

As expected, there are changes in the chemical composition as a function of refining pressure. The higher refining pressures depress the glass transition temperature of the lignin and can initiate hydrolysis of labile carbohydrate bonds. The decrease in the hemicellulose sugars starts above 8 bar, which corresponds to a temperature of 170°C. Below 8 bar, there is no significant change in the amount of hemicellulose sugars, and only minor changes in the extractive content, suggesting limited hydrolysis of the sugars at the lower pressures.

The relationship between the total crystallinity and refining pressure is shown in Fig. 2a. There was a great deal of scatter in the crystallinity measured with XRD, but there is a general trend of increasing crystallinity with increasing refining pressure. These results are consistent with increased refining pressure leading to a decrease in the concentration of the amorphous cellulose and hemicellulose components, and thus a relative increase in the crystallinity of the fibers. The wet chemical analysis shows a clear loss in the hemicellulose sugars (Fig. 1c–1e). Higher refining pressures are also known to decrease the relative amount of early-wood fibers and ray cells, which can also lead to an increase in the relative crystallinity (Rials et al. 2001). There were also differences in the crystallinity of the fibers based on the age of the original wood (Fig. 2b). Refined fibers from mature wood, average age of 35 years, were more

crystalline than fibers from juvenile wood average age 8 years. Fibers from the transition region, average age 20 years, were also more crystalline than the fibers from juvenile wood. These trends are consistent with prior results (Wang and Chiu 1990).

### *NIR spectroscopy*

Representative NIR spectra of fibers refined at different pressures are shown in Fig. 3. As expected, the absorbance in the visible region of the spectra increases, which is consistent with a darkening of the fibers as the refining pressure increased. However, there are few, if any, obvious changes in the overtone and combination regions of the near infrared spectrum that can be assigned to chemical changes in the samples.

The NIR spectra were also used to predict the chemical changes in the fibers. The results from these predictions are shown in Table 1. In general, there is a good correlation between the NIR spectra and the chemical composition of the fibers. The notable exception is the poor correlation between the NIR spectra and measured lignin content. In prior work, the correlation between the measured lignin content and the NIR spectra has been reported to be very strong, generally above 0.85 (Kelley et al. 2004; McLellan et al. 1991; Newman et al. 1994; Raymond et al. 2001; Schimleck et al. 1997).

In the case of these refined fibers, there are two possible explanations for the poor correlation between the NIR spectra and lignin content. Both explanations involve changes in the structure lignin caused by the refining process. Changes in the lignin structure that make the lignin more heterogeneous generally decrease the quality of the correlations since there are more chemical features in the NIR spectra that must be accommodated in the PLS model. This trend has been seen though generally lower correlations between the measured and predicted lignin content in hardwoods versus softwoods. The second explanation involves the actual measured lignin content used for the calibration model. The lignin content measured by the tradi-

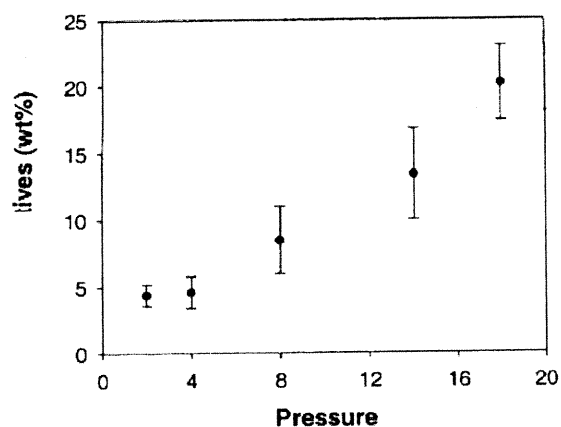


Figure 1a.

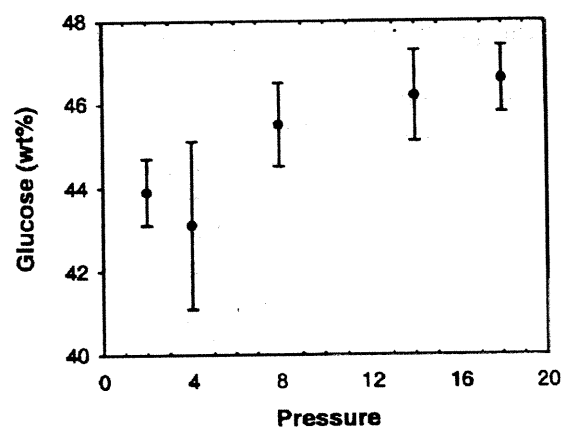


Figure 1b.

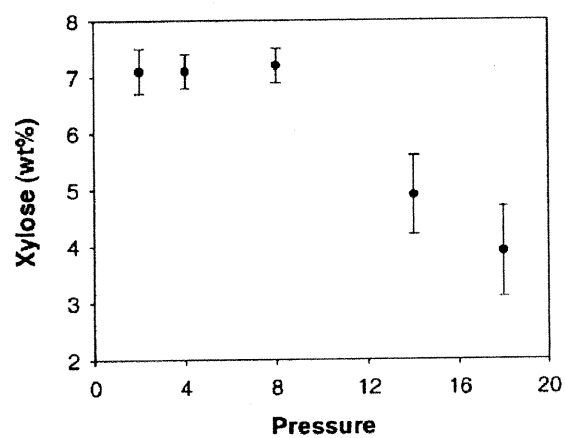


Figure 1c.

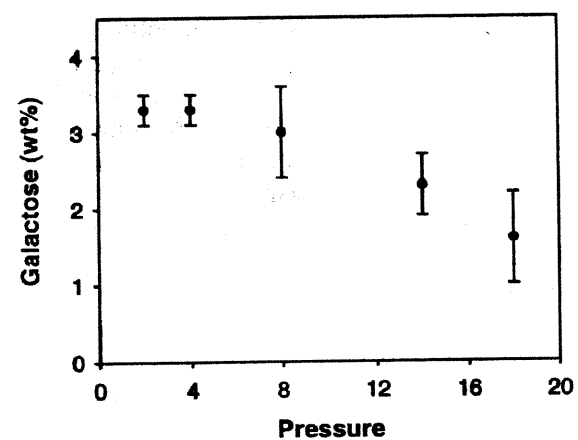


Figure 1d.

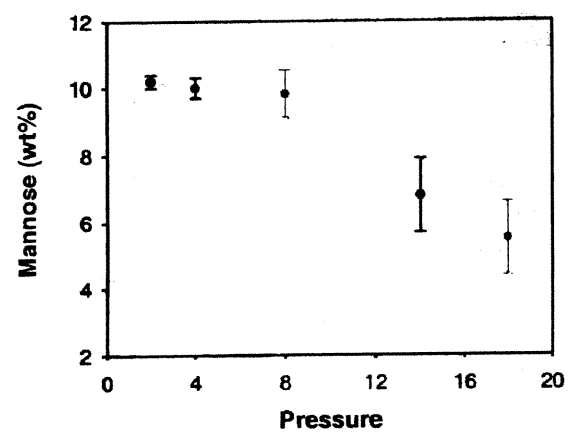


Figure 1e.

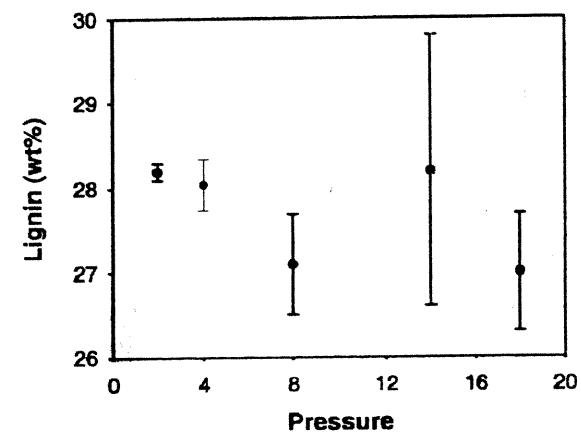


Figure 1f.

FIG. 1. Changes in chemical composition as a function of refining pressure (a) extractives, (b) glucose, (c) xylose, (d) galactose, (e) mannose, (f) lignin.



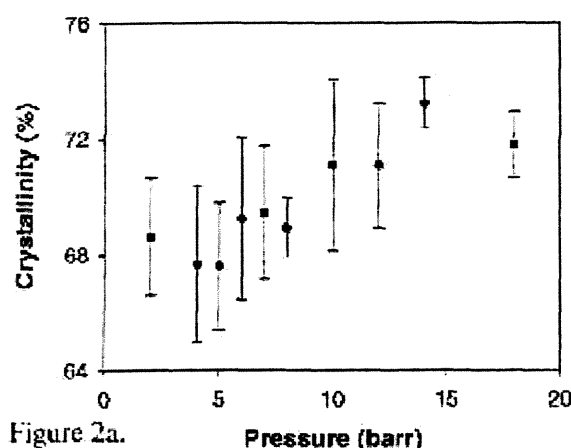


Figure 2a.

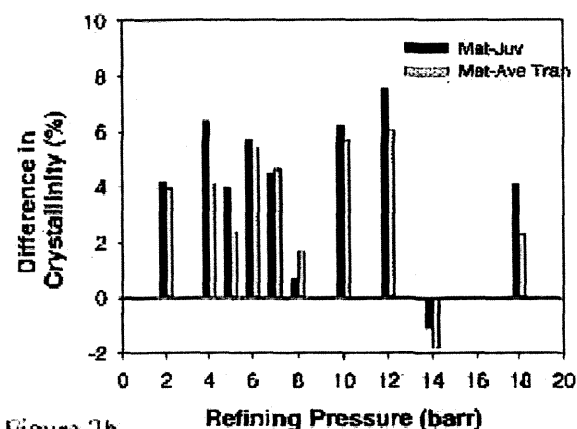


Figure 2b.

Fig. 2. Changes in (a) XRD measured crystallinity for all samples as a function of refining pressure and (b) difference in crystallinity between mature wood (greater than 35 years) and juvenile wood (less than 8 years) and mature wood and transition wood (average age 20 years) with refining pressure.

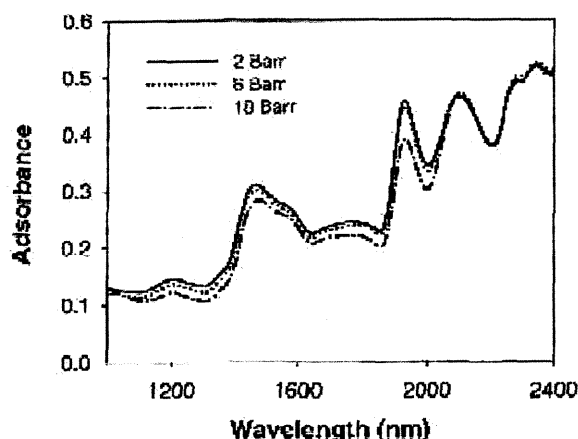


Fig. 3. NIR spectra of mature wood refined at 2, 8, and 18 barr.

TABLE I. Correlations and normalized RMSEP for PLS models predicting the chemical composition, crystallinity and refining pressure of the fibers from NIR spectra, and XRD patterns.

Component	R	Normalized RMSEP	PCs
From NIR spectra			
Extractives	0.92	0.19	2
Glucose	0.88	0.02	4
Mannose	0.95	0.08	4
Galactose	0.78	0.07	4
Xylose	0.91	0.12	5
Lignin	0.25	0.25	2
Refining Pressure	0.93	0.18	2
Crystallinity	0.52	0.15	2
From XRD Patterns			
Refining Pressure	0.91	0.13	5
Crystallinity	0.94	0.02	5

tional wet chemical methods covers a very narrow range of values (26.2 to 28.3, with one sample above 29.8). These Klason lignin analyses used in this study are optimized for a standard softwood lignin, and the refining process may generate non-soluble or soluble lignin structures with uncommon chemical features, that complicate the wet chemical analysis.

Table I also shows the results of a PLS model for refining pressure based in the NIR spectra. There is a strong relationship ( $r = 0.93$ ) between

the measured refining pressure and the refining pressure predicted from the NIR spectra. Given the well-defined changes in the chemical composition as a function of refining pressure (Fig. 1), it is not surprising that the NIR spectra also indicate the effects of refining pressure. The relationship between the total crystallinity and NIR spectra is also shown in Table I. The poor correlation between the NIR spectra and percent

crystallinity was also somewhat surprising. Prior work has shown a good correlation between NIR spectra and the microfibril angle of the cellulose crystallites (Kelley et al. 2004). Microfibril angle of the cellulose crystallites and total crystallinity are different features but similar enough that we had anticipated that the NIR spectra would contain some information on the total crystallinity.

The regression coefficients for the PLS models of refining pressure and crystallinity are shown in Fig. 4. The regression coefficients for both the refining pressure and crystallinity are very similar, indicating that changes in the physical and chemical features observed with the NIR are very similar. These regression coefficients are consistent with changes in carbohydrate hydrogen bonding patterns, but it is impossible to assign these changes to specific carbohydrates.

#### XRD patterns

The crystallinity index of cellulose and wood fibers is commonly measured with XRD, and the XRD patterns for the refined fibers in the current study are shown in Fig. 5. There are two major peaks in the XRD patterns corresponding to the 101 and 002 crystal planes, at 17 and 22°, respectively.

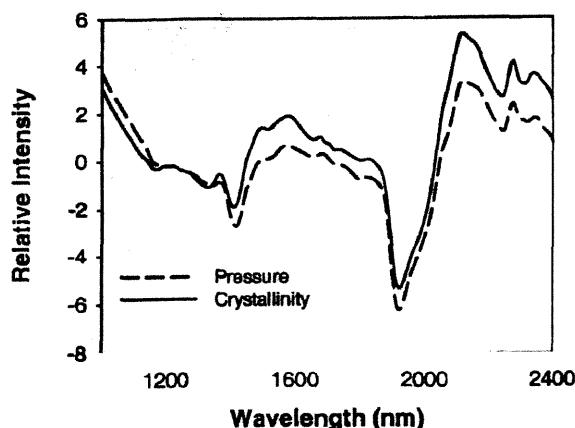


FIG. 4. Regression coefficients from PLS models based on NIR spectra for refining pressure and crystallinity.

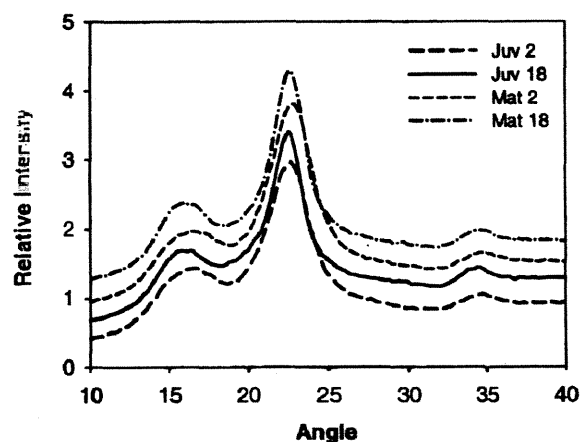


FIG. 5. XRD patterns for juvenile and mature wood refined at 2 and 18 bar.

PLS methods were used to correlate changes in the XRD patterns with the crystallinity index and refining pressure, and these results are also shown in Table 1. There is a high correlation between changes in the XRD patterns and the total crystallinity, which is not surprising. However, there is also a strong relationship between changes in the XRD patterns and the refining pressure used in the preparation of the fibers. So while there is only a modest relationship between the total crystallinity and refining pressure (Fig. 2a), a PLS analysis based on the raw XRD patterns is able to identify subtle shifts in the XRD patterns that are highly correlated with the refining pressure.

Again the PLS analysis also provides the regression coefficients that indicate the specific XRD features that are responsible for the correlations between the XRD patterns, and total crystallinity and refining pressure. The regression coefficients are shown in Fig. 6, along with the averaged XRD patterns for all the fibers refined at 2 and 4 bar, and all the fibers refined at 14 and 18 bar. The regression coefficients for both the crystallinity and the refining pressure show a clear shift in intensity to higher angles for the 002 peak. There is also a less pronounced shift in the regression coefficients of refining pressure to higher angles in the 101 peak.

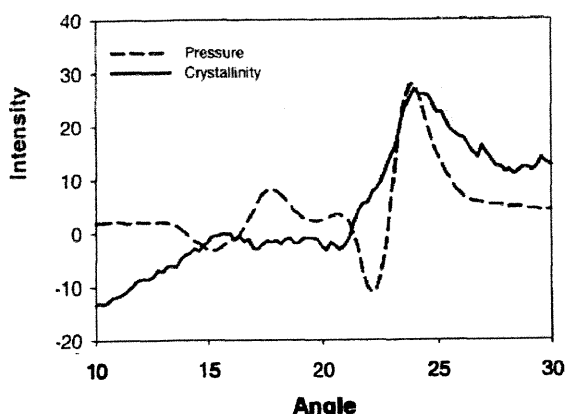


FIG. 6. Regression coefficients from PLS models based on XRD patterns for refining pressure and crystallinity.

### CONCLUSIONS

A series of MDF fibers were prepared using different refining pressures and chips with different average ages. The chemical composition and crystallinity of the refined fibers changed as a function of the refining pressure. Specifically, the extractive and glucose contents increased, while the mannose, xylose, and galactose concentrations decreased with increased refining pressure. The average crystallinity of the fibers also increased with increasing refining pressure. All of these changes were more pronounced above 8 bar refining pressure. The measured lignin content was highly variable and did not show any trends as a function of refining pressure. Across all of the refining pressures the crystallinity of the fibers generally increased with increasing age of the chips. The increase in crystallinity was greatest moving from fibers prepared from the juvenile wood (8 years old) to transition wood (16–24 years old).

NIR and XRD analyses were conducted on the refined fibers. These data were subjected to PLS analysis to monitor the effects of refining pressure, and changes in the chemical composition and crystallinity of the fibers. Both analytical tools could predict changes in the fibers as a function of refining pressure. NIR was effective for predicting the chemical composition, except lignin content. Only XRD was effective for pre-

dicting the overall crystallinity of the refined fibers.

### ACKNOWLEDGMENTS

Support from USDA-Forest Service-Southern Research Station and the U.S. Department of Energy, Office of Industrial Technology Agenda 2020 program, is gratefully acknowledged.

### REFERENCES

- AHTEE, M., T. PAAKKARI, K. PUIKKONEN, AND T. HATTULA. 1980. Crystallinity measurements on thermomechanical pulp by X-ray diffraction. *Paperi ja Puu* 1980 (4a):167–174.
- , T. HATTULA, J. MANGS, AND T. PAAKKARI. 1983. An X-ray diffraction method for determination of crystallinity in wood pulp. *Paperi ja Puu* 1983(8):475–480.
- AMERICAN SOCIETY FOR TESTING MATERIALS (ASTM). 1999. Standard test methods for evaluating properties of wood-base fiber and particle panel materials. ASTM D 1037–99. American Society for Testing and Materials, West Conshohocken, PA.
- ANONYMOUS. 2000. The Unscrambler 7.6, User Manual, Corvallis OR, CAMO Inc., 2000.
- BANG, Y. S. LEE, J. PARK, AND H. CHO. 1999. Effect of coagulation on fine structure of regenerated cellulosic films made from cellulose/N-methylmorpholine-N-oxide/H<sub>2</sub>O systems. *J. Appl. Polym. Sci.* 73:2681–2690.
- ELDER, T., T. G. RIALS, AND L. H. GROOM. 2002. Surface properties of medium density fiberboard furnish. *Proc. 6th Pacific Rim Bio-Based Composites Symposium*. Portland, OR.
- GABRIELSSON, J., N. O. LINDBERG, AND T. LUNDSTEDT. 2002. Multivariate methods in pharmaceutical applications. *J. Chemometrics* 16:141–160.
- GOSWAMI, T., C. SAIKIA, R. BARUAH, AND C. SHARMA. 1996. Characterization of pulp obtained from *Populus deltoides* plants of different ages using IR, XRD, and SEM. *Bioresource Technol.* 57 (2):209–214.
- HINDELEH, A. M., AND D. J. JOHNSON. 1972. Crystallinity and crystallite size measurement in cellulose fibres: 1. Ramie and fortisan. *Polymer* 13(9):423–430.
- HOFFMEYER, P., AND J. PEDERSEN. 1995. Evaluation of density and strength of Norway spruce wood by near infrared reflectance spectroscopy. *Holz Roh-Werkst* 53:165–170.
- HU, X., AND Y.-L. HSIEH. 1996. Crystalline structure of developing cotton fibers. *J. Polym. Sci.: Part B: Polymer Physics* 34:1451–1459.
- KELLEY, S. S., T. G. RIALS, R. SNELL, L. H. GROOM, AND A. SLUITER. 2003. Use of Near Infrared Spectroscopy to measure the chemical and mechanical properties of solid wood. *Wood Sci. Technol.* In Press.

- MARTENS, H., AND T. NAES. 1991. Multivariate calibration. John Wiley & Sons, Chichester, England. 419 pp.
- McLELLAN, T., M. MARTIN, J. ABER, J. MELILLO, K. NADELHOFFER, AND B. DEWEY. 1991. Comparison of wet chemistry and near infrared reflectance measurements of carbon-fraction chemistry and nitrogen concentration of forest foliage. *Can. J. For. Res.* 21:1689–1693.
- MILNE, T. A., H. J. CHUM, F. AGBLEVOR, AND D. K. JOHNSON. 1992. Standardized analytical methods. *Biomass Bioenergy* 2 (1–6):341–366.
- NEWMAN, S., M. SOULIA, J. ABER, B. DEWEY, AND A. RICCA. 1994. Analyses of forest foliage I: Laboratory procedures for proximate carbon fractionation and nitrogen determination. *J. Near Infrared Spec.* 2:5–14.
- RAMOS, L. P., A. FILHO, F. DESCHAMPS, AND J. SADDLER. 1999. The effect of *Trichoderma* cellulases on the fine structure of a bleached softwood kraft pulp. *Enzyme Microb. Technol.* 24:371–380.
- RAYMOND, C., L. SCHIMLECK, A. MUNERI, AND A. MICHELL. 2001. Nondestructive sampling of *Eucalyptus globules* and *E. nitens* for wood properties. III. Predicted pulp yield using near infrared reflectance analysis. *Wood Sci. Technol.* 35 (3):203–215.
- RIALS, T. G., L. H. GROOM, W. TZE, D. J. GARDNER, AND R. SNELL. 2001. Effect of refining on the surface characteristics of loblolly pine fibers. *Abstr. Pap.-Am. Chem. Soc.* 221st CELL-049.
- SCHIMLECK, L., P. WRIGHT, A. MICHELL, AND A. WALLIS. 1997. Near Infrared spectra and chemical compositions of *E. globules* and *E. nitens* plantation woods. *Appita J.* 50 (1):40–46.
- SEGA, L., J. J. CREELY, A. E. MARTIN, JR., AND C. M. CONRAD. 1959. An empirical method for estimating the degree of crystallinity of native cellulose using the X-ray diffractometer. *Textile Res. J.* 1959(October):786–794.
- SNELL, R., L. H. GROOM, AND T. G. RIALS. 2001. Characterizing the surface roughness of thermomechanical pulp fibers with atomic force microscopy. *Holzforschung* 55(5):511–520.
- THUMM, A., AND R. MEDER. 2001. Stiffness prediction of radiata pine clearwood test pieces using near infrared spectroscopy. *J. Near Infrared Spec.* 9:117–122.
- TYGESEN, L. 1994. Determination of dry matter content basic density of Norway spruce by near infrared reflectance and transmittance spectroscopy. *J. Near Infrared Spec.* 2:127–135.
- USDA. 1999. Wood Handbook. Wood as an Engineering Material. General Technical Report FPL-GTR-113.
- WANG, S. Y., AND C. M. CHIU. 1990. The wood properties of Japanese cedar originated by seed and vegetative reproduction in Taiwan. 4. The variation of the degree of crystallinity cellulose. *Mokuzai Gakkaishi* 36(11):909–916.